

LOCTITE® SI 5031™

Known as LOCTITE® 5031™
July 2021

PRODUCT DESCRIPTION

LOCTITE® SI 5031™ provides the following product characteristics:

Technology	Silicone
Chemical Type	Acetoxysilicone
Appearance (uncured)	Light yellow, translucent liquid
Fluorescence	Positive under UV light
Viscosity	Self-levelling liquid
Cure	Ultraviolet (UV) / Visible light
Secondary Cure	Moisture for shadowed areas
Application	Potting, Coating or Sealing
Specific Benefits	Self-leveling for uniform cavity fill

LOCTITE® SI 5031™ is a one component, flowable UV and visible light curable silicone adhesive specially designed for potting, coating, and sealing of various automotive, electronic, military, and industrial components. It also has a secondary moisture cure mechanism for curing in shadowed areas. Upon exposure to sufficient UV / visible light or atmospheric moisture, this product forms a medium strength, flexible sealant.

TYPICAL PROPERTIES OF UNCURED MATERIAL

Specific Gravity @ 25 °C	1.01
Viscosity, Brookfield - RTV, 25 °C, , mPa·s (cP):	5,800
Spindle 3, speed 10 rpm	

TYPICAL CURING PERFORMANCE

Normal processing conditions will include exposure to sufficient UV/visible light irradiance to effectively cure the material. Surface and/or atmospheric moisture will promote the cure of material in shadowed regions. Although functional strength is developed almost instantly due to the UV/visible curing nature of LOCTITE® SI 5031™, increased cure properties are developed during 72 hours at ambient conditions.

Surface Cure

When curing with sufficient UV/visible light irradiance, exposed material cures dry to the touch in seconds.

Skin Over Time

Skin over time is the time the surface of the adhesive forms a skin upon exposure to atmospheric moisture at 23°C/ 50% RH.

Skin Over Time, minutes	20
Cured @ 23 °C	

Tack Free Time

Tack Free time is the time required to achieve a tack free surface.

Tack Free Time,seconds	20
70 mW/cm ² , measured @ 365nm	


Depth of Cure

Depth of cure, mm:	
90seconds @ 70 mW/cm ² , measured @ 365 nm	20

Depth of Cure (light)

Shadowed areas rely on surface and/or atmospheric moisture to effect cure. Rapid depth of cure can be attained with focused UV and/or visible light. The following graph shows the cure response of some

typical light sources as a function of irradiance after 60 seconds. The following data table shows the depth of cure obtained upon exposure to different light sources and intensities over time.


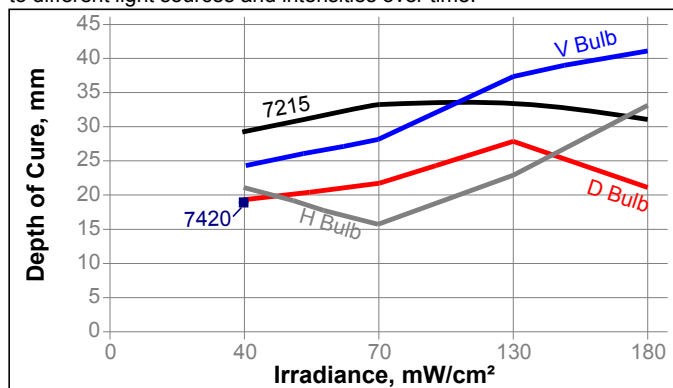


Light Source	Irradiance UV/VIS	Depth of Cure, mm		
		30 sec.	60 sec.	90 sec.
7411 UV (metal halide)	180/58	7	23	31
7411 V (visible enhanced metal halide)	40/98	8	20	23
7215 (300-watt medium pressure Hg arc)	75/95	23	33	41
Electrodeless V bulb	71/120	17	28	39
Electrodeless D bulb	76/50	10	22	33
Electrodeless H bulb	71/68	5	16	24
Electrodeless H+ bulb	74/64	9	21	28
7735 (50-watt high pressure Hg arc)	890/410	---	13	17
7740 (100-watt high pressure Hg arc)	800/410	3	14	17
7760 (200-watt high pressure Hg arc)	1,100/460	---	9	13
7700 (LED)	12/31	---	8	13
7420 (visible arc lamp)	20/40	8	---	27
7500 (fluorescent lamp)	40/0	---	2	4

Note: Irradiance measured with 7011-A (UV) & 7011-V (VIS) dosimeters

Depth of Cure (moisture only)

Moisture cure of shadowed areas rely on surface and/or atmospheric moisture to effect cure. The typical depth of cure from moisture only versus time (days) at 23 °C and 50% relative humidity is shown in the graph below.

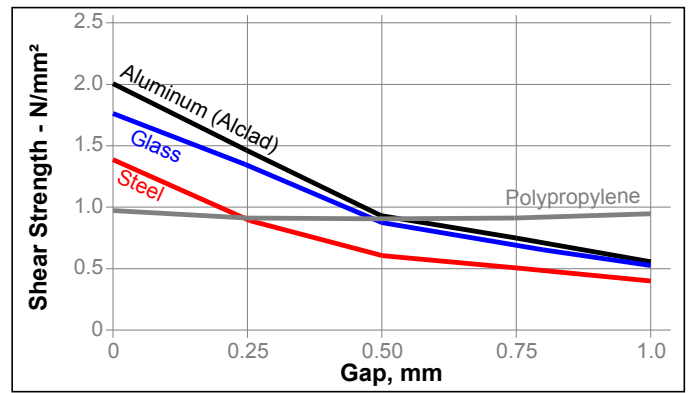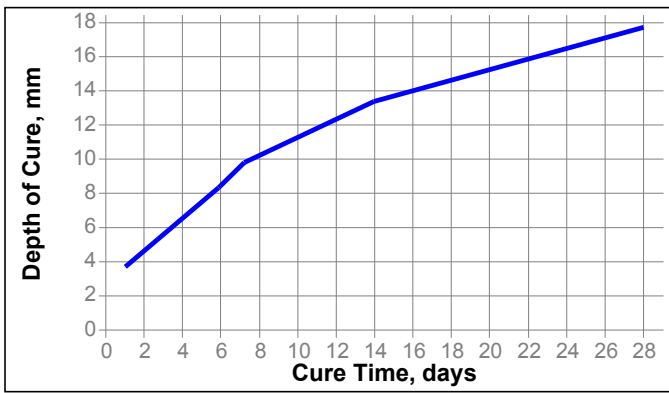

TYPICAL PERFORMANCE OF CURED MATERIAL

Cured for 60 seconds @ 70 mW/cm², measured @ 365 nm, followed by 72 hours @ 23°C / 50% RH (Isopropyl alcohol wiped substrates).

Adhesive Properties

Lap Shear Strength ISO 4587:

Aluminum (Alclad) to Glass	N/mm ²	2
	(psi)	(290)
Steel to Glass	N/mm ²	1
	(psi)	(150)
Glass to Glass	N/mm ²	2
	(psi)	(290)
Polycarbonate to Polycarbonate	N/mm ²	0.1
	(psi)	(15)
Polycarbonate to Glass	N/mm ²	0.4
	(psi)	(60)
Polycarbonate to Aluminum	N/mm ²	0.2
	(psi)	(30)
Polycarbonate to Steel	N/mm ²	0.5
	(psi)	(70)
PVC to Glass	N/mm ²	0.8
	(psi)	(120)
PVC to Polycarbonate	N/mm ²	0.4
	(psi)	(60)
Polybutylene Terephthalate (PBT) to Glass	N/mm ²	0.8
	(psi)	(120)
Polybutylene Terephthalate (PBT) to Polycarbonate	N/mm ²	0.2
	(psi)	(30)
ABS to Glass	N/mm ²	0.4
	(psi)	(60)
ABS to Polycarbonate	N/mm ²	0.3
	(psi)	(40)
Nylon to Glass	N/mm ²	5
	(psi)	(725)
Nylon to Polycarbonate	N/mm ²	0.1
	(psi)	(15)

Shear Strength vs. Gap Thickness

Cured for 60 seconds @ 70 mW/cm², measured @ 365 nm, followed by 7 days @ 23°C / 50% RH.

TYPICAL ENVIRONMENTAL RESISTANCE

Cured for 60 seconds @ 70 mW/cm², measured @ 365 nm, followed by 7 days @ 23°C / 50% RH.

Heat Aging

Aged at temperature indicated and tested @ 23 °C

Aged @ 177 °C for 168 hours:

Change in Durometer, Points (Initial = 36)	-8
Change in Tensile Strength, %	-6
Change in Elongation, %	18
Weight Loss, %	-3

Aged @ 233 °C for 168 hours:

Change in Durometer, Points (Initial = 36)	24
Change in Tensile Strength, %	61
Change in Elongation, %	-66
Weight Loss, %	-3

Typical Fluid Immersion Properties

Aged @ 100 °C for 168 hours:

Ethylene glycol/water, 50:50:	
Change in Durometer, Points (Initial = 36)	-14
Change in Tensile Strength, %	-43
Change in Elongation, %	25
Volume Swell, %	-2

Propylene glycol/water (Dex-Cool®), 50:50:

Change in Durometer, Points (Initial = 36)	-16
Change in Tensile Strength, %	-29
Change in Elongation, %	42
Volume Swell, %	-2

Aged @ 150 °C for 70 hours:

ASTM IRM 903 oil:	
Change in Durometer, Points (Initial = 36)	-20
Change in Tensile Strength, %	-26
Change in Elongation, %	14
Volume Swell, %	47

Aged @ 150 °C for 168 hours:

5W30 oil:

Change in Durometer, Points (Initial = 36)	-31
Change in Tensile Strength, %	-55
Change in Elongation, %	20
Volume Swell, %	25

ASTM IRM 901 oil:

Change in Durometer, Points (Initial = 36)	-21
Change in Tensile Strength, %	31
Change in Elongation, %	330
Volume Swell, %	6

ASTM IRM 902 oil:

Change in Durometer, Points (Initial = 36)	-13
Change in Tensile Strength, %	-16
Change in Elongation, %	23
Volume Swell, %	8

ATF (Dexron® III):

Change in Durometer, Points (Initial = 36)	-31
Change in Tensile Strength, %	-61
Change in Elongation, %	94
Volume Swell, %	23

GENERAL INFORMATION

This product is not recommended for use in pure oxygen and/or oxygen rich systems and should not be selected as a sealant for chlorine or other strong oxidizing materials.

For safe handling information on this product, consult the Safety Data Sheet (SDS).

Directions For Use

1. For best performance bond surfaces should be clean and free from grease.
2. The product is light sensitive; exposure to daylight, UV light and artificial lighting should be kept to a minimum during storage and handling.
3. The product should be dispensed from applicators with black feedlines.
4. The product is designed to be initially cured with UV light at a minimum irradiance of 30 mW/cm² for approximately 20 seconds, increased exposure may be required for curing deeper sections.
5. Functional strength is achieved almost instantly.
6. Full performance properties will develop over 72 hours.
7. Moisture curing begins immediately after the product is exposed to the atmosphere, therefore parts to be assembled should be mated within a few minutes after the product is dispensed.
8. Excess material can be easily wiped away with non-polar solvents.
9. For fully automatic applications a volumetric dispensing system is recommended.

Storage

Store product in the unopened container in a dry location. Storage information may be indicated on the product container labeling.

Optimal Storage: 8 °C to 21 °C. Storage below 8 °C or greater than 28 °C can adversely affect product properties.

Material removed from containers may be contaminated during use. Do not return product to the original container. Henkel Corporation cannot assume responsibility for product which has been contaminated or stored under conditions other than those previously indicated. If additional information is required, please contact your local Henkel representative.

Product Specification

The technical data contained herein are intended as reference only and are not considered specifications for the product. Product specifications are located on the Certificate of Analysis or please contact Henkel representative.

Approval and Certificate

Please contact your local Henkel representative for related approval or certificate of this product.

Data Ranges

The data contained herein may be reported as a typical value. Values are based on actual test data and are verified on a periodic basis.

Temperature/Humidity Ranges: 23 °C / 50% RH = 23±2 °C / 50±5% RH

Conversions

(°C x 1.8) + 32 = °F
 kV/mm x 25.4 = V/mil
 mm / 25.4 = inches
 µm / 25.4 = mil
 N x 0.225 = lb
 N/mm x 5.71 = lb/in
 N/mm² x 145 = psi
 MPa x 145 = psi
 N·m x 8.851 = lb·in
 N·m x 0.738 = lb·ft
 N·mm x 0.142 = oz·in
 mPa·s = cP

Disclaimer

The information provided in this Technical Data Sheet (TDS) including the recommendations for use and application of the product are based on our knowledge and experience of the product as at the date of this TDS. The product can have a variety of different applications as well as differing application and working conditions in your environment that are beyond our control. Henkel is, therefore, not liable for the suitability of our product for the production processes and conditions in respect of which you use them, as well as the intended applications and results. We strongly recommend that you carry out your own prior trials to confirm such suitability of our product.

Any liability in respect of the information in the Technical Data Sheet or any other written or oral recommendation(s) regarding the concerned product is excluded, except if otherwise explicitly agreed and except in relation to death or personal injury caused by our negligence and any liability under any applicable mandatory product liability law.

In case products are delivered by Henkel Belgium NV, Henkel Electronic Materials NV, Henkel Nederland BV, Henkel Technologies France SAS and Henkel France SA please additionally note the following:

In case Henkel would be nevertheless held liable, on whatever legal ground, Henkel's liability will in no event exceed the amount of the concerned delivery.

In case products are delivered by Henkel Colombiana, S.A.S. the following disclaimer is applicable:

The information provided in this Technical Data Sheet (TDS) including the recommendations for use and application of the product are based on our knowledge and experience of the product as at the date of this TDS. Henkel is not liable for the suitability of our product for the production processes and conditions in respect of which you use them, as well as the intended applications and results. We strongly recommend that you carry out your own prior trials to confirm such suitability of our product.

Any liability in respect of the information in the Technical Data Sheet or any other written or oral recommendation(s) regarding the concerned product is excluded, except if otherwise explicitly agreed and except in relation to death or personal injury caused by our negligence and any liability under any applicable mandatory product liability law.

In case products are delivered by Henkel Corporation or Henkel Canada, Inc. the following disclaimer is applicable:

The data contained herein are furnished for information only and are believed to be reliable. We cannot assume responsibility for the results obtained by others over whose methods we have no control. It is the user's responsibility to determine suitability for the user's purpose of any production methods mentioned herein and to adopt such precautions as may be advisable for the protection of property and of persons against any hazards that may be involved in the handling and use thereof. In light of the foregoing, **Henkel Corporation specifically disclaims all warranties expressed or implied, including warranties of merchantability or fitness for a particular purpose, arising from sale or use of Henkel Corporation's products. Henkel Corporation specifically disclaims any liability for consequential or incidental damages of any kind, including lost profits.** The discussion herein of various processes or compositions is not to be interpreted as representation that they are free from domination of patents owned by others or as a license under any Henkel Corporation patents that may cover such processes or compositions. We recommend that each prospective user test his proposed application before repetitive use, using this data as a guide. This product may be covered by one or more United States or foreign patents or patent applications.

Trademark usage

Except as otherwise noted, all trademarks in this document are trademarks of

Henkel Corporation in the U.S. and elsewhere. ® denotes a trademark registered in the U.S. Patent and Trademark Office.

